


Cutting Charts

The cutting charts shown on the following pages are intended to give the operator the best starting point to use when making a cut on a particular material type and thickness. Small adjustments may have to be made to achieve the best cut. Also, remember that the arc voltage must be increased as the electrode wears in order to maintain the correct cutting height.

Cutting Chart Index

Material	Current	Plasma Gas	Shield Gas	Copper Electrode	Silver Electrode
Mild Steel	30 Amps	Oxygen	Oxygen	Page 4-25	
Mild Steel	50 Amps	Oxygen	Oxygen or Air	Page 4-26	
Mild Steel	70 Amps	Oxygen	Air	Page 4-27	
Mild Steel	100 Amps	Oxygen	Air	Page 4-28	
Mild Steel	150 Amps	Oxygen	Air	Page 4-29	
Mild Steel	200 Amps	Oxygen	Air	Page 4-30	Page 4-51
Mild Steel	275 Amps	Oxygen	Air	Page 4-31	Page 4-52
Stainless Steel	30 Amps	Air	Air	Page 4-32	
Stainless Steel	50 Amps	Air	Nitrogen	Page 4-33	
Stainless Steel	70 Amps	H17	Nitrogen	Page 4-34	
Stainless Steel	70 Amps	Air	Nitrogen	Page 4-35	
Stainless Steel	100 Amps	H17	Nitrogen	Page 4-36	
Stainless Steel	100 Amps	Air	Nitrogen	Page 4-37	
Stainless Steel	150 Amps	H17	Nitrogen	Page 4-38	
Stainless Steel	150 Amps	Air	Nitrogen	Page 4-39	
Stainless Steel	200 Amps	H17	Nitrogen	Page 4-40	
Stainless Steel	200 Amps	Air	Nitrogen	Page 4-41	Page 4-53
Stainless Steel	260 Amps	H17	Nitrogen	Page 4-42	
Stainless Steel	275 Amps	Air	Nitrogen	Page 4-43	
Aluminum	30 Amps	Air	Nitrogen	Page 4-44	
Aluminum	50 Amps	Air	Nitrogen	Page 4-45	
Aluminum	70 Amps	Air	Nitrogen	Page 4-46	
Aluminum	100 Amps	Air	Nitrogen	Page 4-47	
Aluminum	150 Amps	Air	Nitrogen	Page 4-48	
Aluminum	200 Amps	Air	Nitrogen	Page 4-49	Page 4-54
Aluminum	275 Amps	Air	Nitrogen	Page 4-50	Page 4-55

Mild Steel - 30 Amps - Oxygen Plasma / Oxygen Shield Copper Electrode

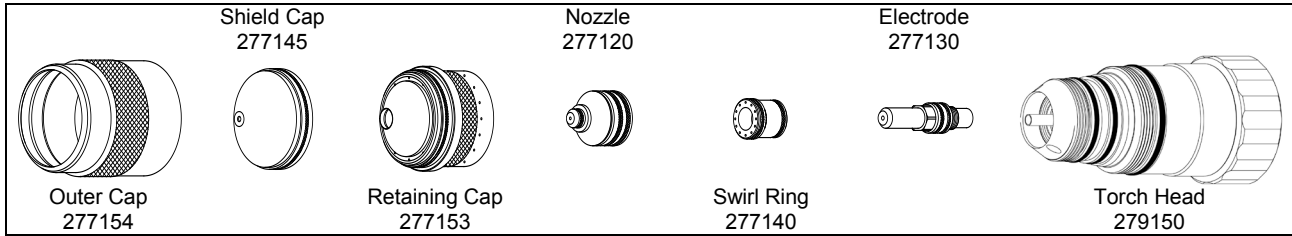

Imperial

Material Thickness		Preflow	Plasma	Shield	Postflow	Arc Voltage	Travel Speed	Cutting Height	Pierce Height	Pierce Time	Kerf Width
(ga)	(in)	(psi)	(psi)	(psi)	(psi)	(volts)	(ipm)	(in)	(in)	(msec)	(in)
20	.036	35	85	6	84	120	105	.080	.110	100	.062
18	.048					121	97	.090			
16	.060					125	78	.105		200	.065
14	.075					126	65				
12	.105					127	55	.120	.125	300	.070
11	.120					129	50				
10	.135					131	40				

Metric


Material Thickness		Preflow	Plasma	Shield	Postflow	Arc Voltage	Travel Speed	Cutting Height	Pierce Height	Pierce Time	Kerf Width
(mm)	(mm)	(psi)	(psi)	(psi)	(psi)	(volts)	(mm/m)	(mm)	(mm)	(msec)	(mm)
1		35	85	6	84	120	2615	2.0	2.8	100	1.6
1.5						124	2020	2.6			
2						126	1615	2.7		200	1.7
2.5						1455					
3						128	1285	2.9	300	1.8	

Marking

Material Thickness			Preflow	Plasma	Shield	Postflow	Travel Speed		Marking Height		Initial Height		Pierce Time
(ga)	(in)	(mm)	(psi)	(psi)	(psi)	(psi)	(ipm)	(mm/min)	(in)	(mm)	(in)	(mm)	(msec)
All Thicknesses			N/A	28	28	N/A	250	6350	.177	4.5	.100	2.5	0

1. Revised on 10/21/2009

Mild Steel - 50 Amps - Oxygen Plasma / Oxygen or Air Shield Copper Electrode

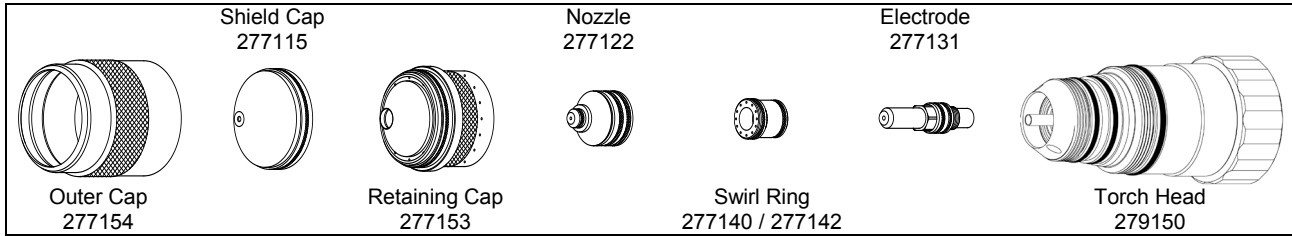

Imperial

Material Thickness		Preflow	Plasma	Shield	Postflow	Arc Voltage	Travel Speed	Cutting Height	Pierce Height	Pierce Time	Kerf Width
(ga)	(in)	(psi)	(psi)	(psi)	(psi)	(volts)	(ipm)	(in)	(in)	(msec)	(in)
Cold-Rolled Steel – Oxygen Shield – Swirl Ring 277140											
12	.105	25	74	12	73	123	70	.120	.135	100	.075
11	.120					126	60	.125		200	.078
10	.135					128	50	.135			
Hot-Rolled Steel – Air Shield – Swirl Ring 277142											
14	.075	25	74	19	73	106	200	.100	.135	100	.075
12	.105						190			200	.080
	.125						180				
10	.135					110	170	.110		300	.085
	3/16					113	105	.140		400	.087
	1/4					117	75	.225			

Metric

Material Thickness		Preflow	Plasma	Shield	Postflow	Arc Voltage	Travel Speed	Cutting Height	Pierce Height	Pierce Time	Kerf Width
(mm)	(mm)	(psi)	(psi)	(psi)	(psi)	(volts)	(mm/m)	(mm)	(mm)	(msec)	(mm)
Cold-Rolled Steel – Oxygen Shield – Swirl Ring 277140											
2.5		25	74	12	73	121	1895	2.9	3.4	100	1.9
3						125	1555	3.1		200	2.0
Hot-Rolled Steel – Air Shield – Swirl Ring 277142											
2.5		25	74	19	73	106	4885	2.5	3.4	100	1.9
3							4660			200	2.0
5						113	2555	3.6		400	2.2
6						116	2075	5.5			


Marking

Material Thickness			Preflow	Plasma	Shield	Postflow	Arc Voltage	Travel Speed		Marking Height	Initial Height	Pierce Time
(ga)	(in)	(mm)	(psi)	(psi)	(psi)	(psi)	(volts)	(ipm)	(mm/min)	(in)	(mm)	(msec)
All Thicknesses			N/A	28	28	N/A	145	250	6350	.147	3.7	.100 2.5 0

1. Revised 10/21/2009

This information is subject to the controls of the Export Administration Regulations [EAR]. This information shall not be provided to non-U.S. persons or transferred by any means to any location outside the United States contrary to the requirements of the EAR.

Mild Steel - 70 Amps - Oxygen Plasma / Air Shield Copper Electrode

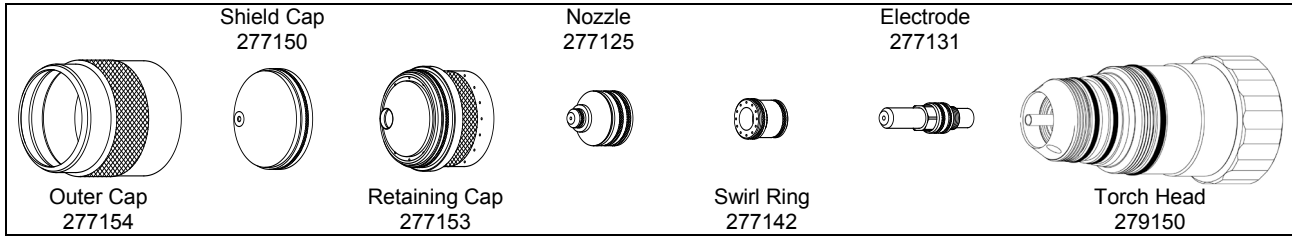

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)
1/8	25	80	35	79	110	190	.100	.150	100	.080
3/16						113		130	.200	
1/4			40		116	120	.110	.225	300	.085
3/8					122	75	.140	.250	400	

Metric


Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
3	25	80	35	79	109	4995	2.5	3.6	100	2.0
5						113		3265	5.1	
6			40		115	3105	2.7	5.5		2.2

Marking

Material Thickness (ga) (in) (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm) (mm/min)	Marking Height (in) (mm)	Initial Height (in) (mm)	Pierce Time (msec)
All Thicknesses	N/A	28	28	N/A	135	250 6350	.096 2.4	.100 2.5	0

1. Revised on 12/01/2009

Mild Steel - 100 Amps - Oxygen Plasma / Air Shield Copper Electrode

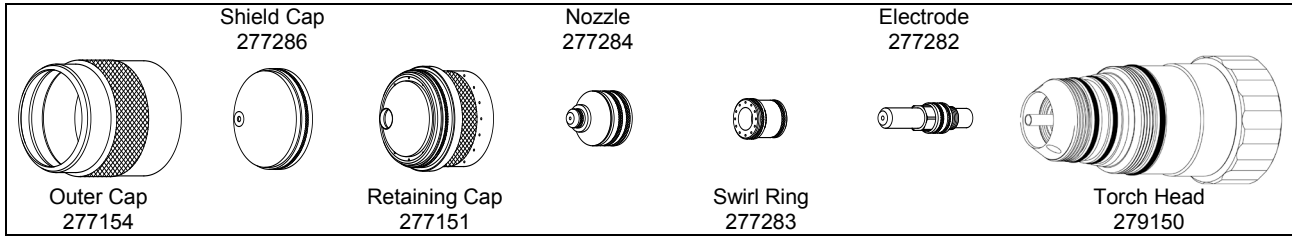

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)
1/4	25	94	26	93	125	150	.090	.200	300	.090
3/8					130	100	.130	.250	400	
1/2						65	.155	.300	500	
5/8					143	47	.185	.325	800	.095
3/4					145	35		.350	1000	

Metric


Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
6	25	94	26	93	124	3950	2.1	4.9	300	2.3
10					130	2405	3.3	6.5	500	
12						1850	3.7	7.3		
16					143	1180	4.7	8.3	1000	2.4
20					145	800		9.0		

Marking

Material Thickness (ga) (in) (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm) (mm/min)	Marking Height (in) (mm)	Initial Height (in) (mm)	Pierce Time (msec)
All Thicknesses	N/A	28	28	N/A	130	250 6350	.100 2.5	.100 2.5	0

* Use an arc transfer height (ignition height) of .200" (5.1 mm) for cutting and .100" (2.5 mm) for marking
1. Revised on 10/21/2009

Mild Steel - 150 Amps – Oxygen Plasma / Air Shield Copper Electrode

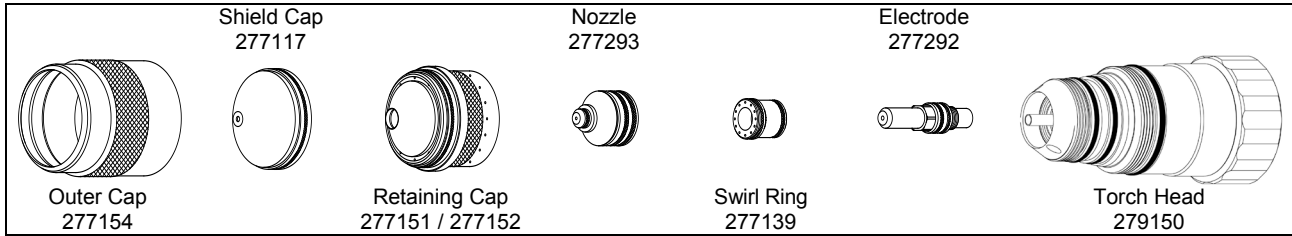

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)
Retaining Cap 277151										
1/4	20	74	30	67	118	165	.105	.200	300	.125
3/8					123	125	.135	.250	400	
1/2					125	90	.140	.300	500	
Retaining Cap 277152										
5/8	20	74	45	67	127	70	.140	.325	600	.130
3/4					130	55		.350	1000	.135
1					134	40	.150	.400	1500	.140
1.25 **					145	25	.200			
1.5 **					155	15	.225			

Metric

Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
Retaining Cap 277151										
6	20	74	30	67	117	4305	2.6	4.9	300	3.2
10					123	3040	3.4	6.5	500	
12					124	2485	3.5	7.3		
Retaining Cap 277152										
16	20	74	45	67	127	1760	3.6	8.3	1000	3.3
20					130	1340		9.0	1500	3.4
25					133	1040	3.7	10.1		
32 **					145	625	5.1	8.9		
38 **					154	385	5.6	8.9		

Marking


Material Thickness (ga) (in) (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm) (mm/min)	Marking Height (in) (mm)	Initial Height (in) (mm)	Pierce Time (msec)
All Thicknesses	N/A	28	28	N/A	135	250 6350	.100 2.5	.100 2.5	0

* Use an arc transfer height (ignition height) of .200" (5.1 mm) for cutting and .100" (2.5 mm) for marking

** Edge start recommended
1. Revised on 12/01/09

This information is subject to the controls of the Export Administration Regulations [EAR]. This information shall not be provided to non-U.S. persons or transferred by any means to any location outside the United States contrary to the requirements of the EAR.

Mild Steel - 200 Amps – Oxygen Plasma / Air Shield Copper Electrode

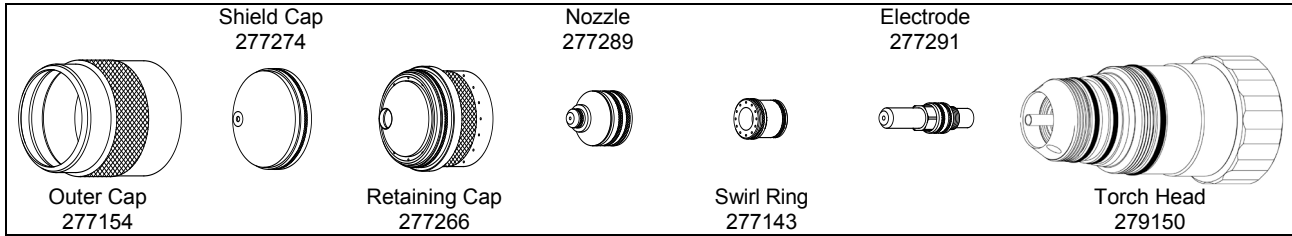

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)
1/4	20	82	58	75	125	230	.040	.200	300	.150
3/8					130	140	.090	.250	400	
1/2					133	120	.115	.300	500	
5/8					137	100	.130	.350	600	.152
3/4					140	75	.150	.400	800	.153
1					147	50	.175	.450	1000	.155
1.25					155	25	.240	.500	1500	
1.5 **					165	17	.300	.350		
1.75 **					175	12	.350		.500	
2.0 **					185	7	.500	.500		.160

Metric

Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
6	20	82	58	75	124	6100	.8	4.9	300	3.8
10					130	3480	2.3	6.5	500	
12					132	3160	2.7	7.3	1000	
16					137	2515	3.3	8.9		800
20					141	1810	3.8	10.3	1500	3.9
25					146	1310	4.3	11.3		
32					155	610	6.1	12.7		4.0
38 **					164	435	7.5	8.9		
45 **					175	295	9.2	9.2	4.1	
50 **					183	195	12.2	12.2		

Marking

Material Thickness (ga) (in) (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm) (mm/min)	Marking Height (in) (mm)	Initial Height (in) (mm)	Pierce Time (msec)
All Thicknesses	N/A	28	28	N/A	120	250 6350	.100 2.5	.100 2.5	0


* Use an arc transfer height (ignition height) of .200" (5.1 mm) for cutting and .100" (2.5 mm) for marking

** Edge start recommended

(Revised 12/01/09)

This information is subject to the controls of the Export Administration Regulations [EAR]. This information shall not be provided to non-U.S. persons or transferred by any means to any location outside the United States contrary to the requirements of the EAR.

Mild Steel - 275 Amps - Oxygen Plasma / Air Shield Copper Electrode

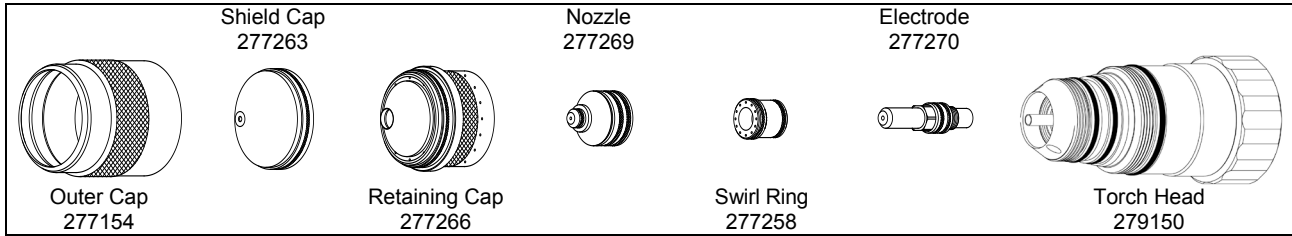

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)
1/2	20	93	70	83	139	125	.140	.300	500	.165
5/8						105	.135	.325	600	
3/4					138	90	.120	.350	800	.170
1										
1.25					150	45	.175	.500	1500	.185
1.50 **										
1.75 **					170	20	.290	.375	.260	
2.00 **										180
2.25 **					185	13	.375	.385		
2.50 **									190	9

Metric

Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
12	20	93	70	83	139	3290	3.6	7.4	500	4.2
16						2650	3.3	8.3	800	
20					138					2190
25						143	1690	4.0	10.1	
32					150					1120
38 **						162	645	5.9	8.9	
45 **					170					495
50 **						178	395	8.7	6.9	
55 **					183					345
60 **						187	285	9.6	9.6	

Marking

Material Thickness (ga) (in) (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm) (mm/min)	Marking Height (in) (mm)	Initial Height (in) (mm)	Pierce Time (msec)
All Thicknesses	N/A	28	28	N/A	108	250 6350	.100 2.5	.100 2.5	0


* Use an arc transfer height (ignition height) of .300" (7.6 mm) for cutting and .100" (2.5 mm) for marking

** Edge start recommended.

(Revised 10/22/09)

This information is subject to the controls of the Export Administration Regulations [EAR]. This information shall not be provided to non-U.S. persons or transferred by any means to any location outside the United States contrary to the requirements of the EAR.

Stainless Steel - 30 Amps - Air Plasma / Air Shield Copper Electrode

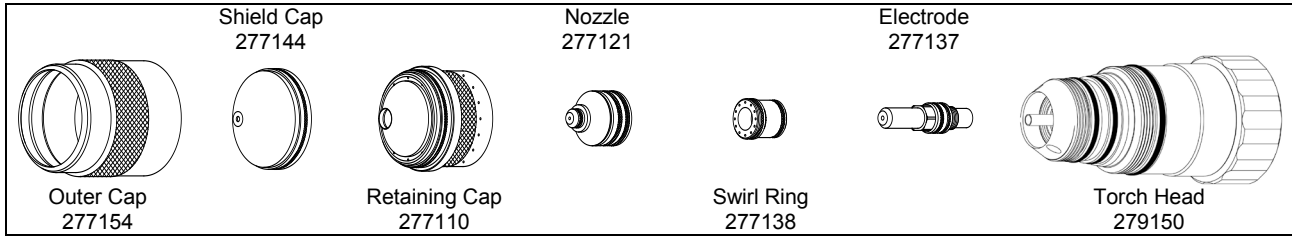

Imperial

Material Thickness		Preflow	Plasma	Shield	Postflow	Arc Voltage	Travel Speed	Cutting Height	Pierce Height	Pierce Time	Kerf Width
(ga)	(in)	(psi)	(psi)	(psi)	(psi)	(volts)	(ipm)	(in)	(in)	(msec)	(in)
20	.036	30	80	30	80	71	200	.020	.050	100	.065
18	.048					74	165	.035			
16	.060					75	125	.025		200	.068
14	.075					75	90	.025			

Metric


Material Thickness		Preflow	Plasma	Shield	Postflow	Arc Voltage	Travel Speed	Cutting Height	Pierce Height	Pierce Time	Kerf Width
(mm)	(mm)	(psi)	(psi)	(psi)	(psi)	(volts)	(mm/m)	(mm)	(mm)	(msec)	(mm)
1		30	80	30	80	71	4855	0.6	1.3	100	1.7
1.5						73	3260	0.9		200	

Marking

Material Thickness			Preflow	Plasma	Shield	Postflow	Arc Voltage	Travel Speed		Marking Height		Initial Height		Pierce Time
(ga)	(in)	(mm)	(psi)	(psi)	(psi)	(psi)	(volts)	(ipm)	(mm/min)	(in)	(mm)	(in)	(mm)	(msec)
All Thicknesses			N/A	28	28	N/A	145	250	6350	.177	4.5	.100	2.5	0

* Use an arc transfer height (ignition height) of .050" (1.3 mm) for cutting and .100" (2.5 mm) for marking
(Revised 12/1/2009)

Stainless Steel - 50 Amps – Air Plasma / Nitrogen Shield Copper Electrode

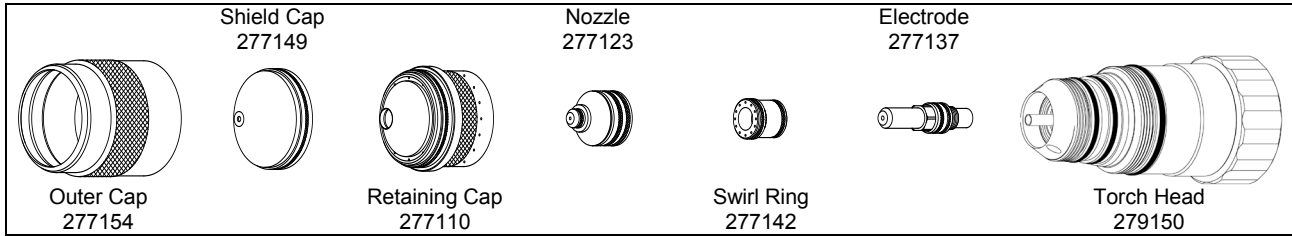

Imperial

Material Thickness		Preflow	Plasma	Shield	Postflow	Arc Voltage	Travel Speed	Cutting Height	Pierce Height	Pierce Time	Kerf Width
(ga)	(in)	(psi)	(psi)	(psi)	(psi)	(volts)	(ipm)	(in)	(in)	(msec)	(in)
14	.075	30	70	40	70	87	105	.035	.070	100	.105
12	.105					88	75				
11	.120					89	65				
10	.135					90	55	.040	.080	300	.110
	3/16					94	50				
	1/4					100	40	.060	.125	400	.115

Metric

Material Thickness		Preflow	Plasma	Shield	Postflow	Arc Voltage	Travel Speed	Cutting Height	Pierce Height	Pierce Time	Kerf Width
(mm)	(mm)	(psi)	(psi)	(psi)	(psi)	(volts)	(mm/m)	(mm)	(mm)	(msec)	(mm)
2		30	70	40	70	87	2565	.9	1.8	100	2.7
2.5	2080										
3	1685										
5	94					1235	1.0	2.1	400	2.8	
6	98					1075	1.3	2.9			

Marking


Material Thickness			Preflow	Plasma	Shield	Postflow	Travel Speed		Marking Height		Initial Height		Pierce Time
(ga)	(in)	(mm)	(psi)	(psi)	(psi)	(psi)	(ipm)	(mm/min)	(in)	(mm)	(in)	(mm)	(msec)
All Thicknesses			N/A	28	25	N/A	250	6350	.147	3.7	.100	2.5	0

* Use an arc transfer height (ignition height) of .070" (1.8 mm) for cutting and .100" (2.5 mm) for marking
(Revised 10/21/2009)

This information is subject to the controls of the Export Administration Regulations [EAR]. This information shall not be provided to non-U.S. persons or transferred by any means to any location outside the United States contrary to the requirements of the EAR.

Stainless Steel - 70 Amps - H17 Plasma / Nitrogen Shield Copper Electrode

This gas combination gives the best cut quality and minimum dross levels

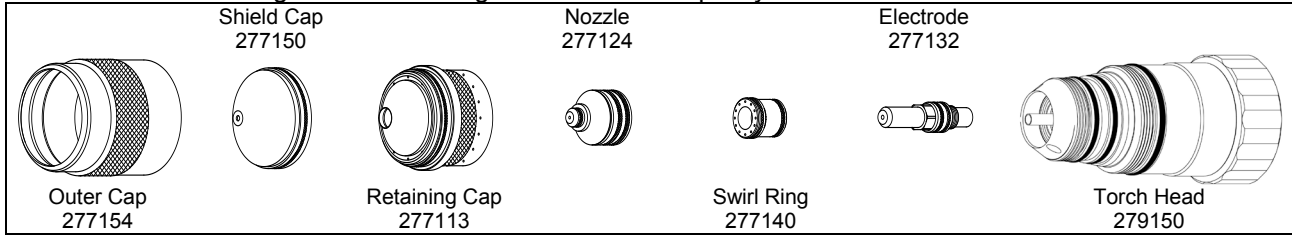

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)
3/16	35	60	36	60	135	80	.100	.200	300	.090

Metric

Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
5	35	60	36	60	135	2030	2.5	5.1	300	2.3


Marking

Material Thickness			Preflow	Plasma	Shield	Postflow	Arc Voltage	Travel Speed		Marking Height		Initial Height		Pierce Time
(ga)	(in)	(mm)	(psi)	(psi)	(psi)	(psi)	(volts)	(ipm)	(mm/min)	(in)	(mm)	(in)	(mm)	(msec)
All Thicknesses			N/A	28	25	N/A	135	250	6350	.096	2.4	.100	2.5	0

* Use an arc transfer height (ignition height) of .150" (3.8 mm) for cutting and .100" (2.5 mm) for marking
(Revised 12/1/2009)

Stainless Steel - 70 Amps - Air Plasma / Nitrogen Shield Copper Electrode

This gas combination gives medium cut quality and minimum dross levels

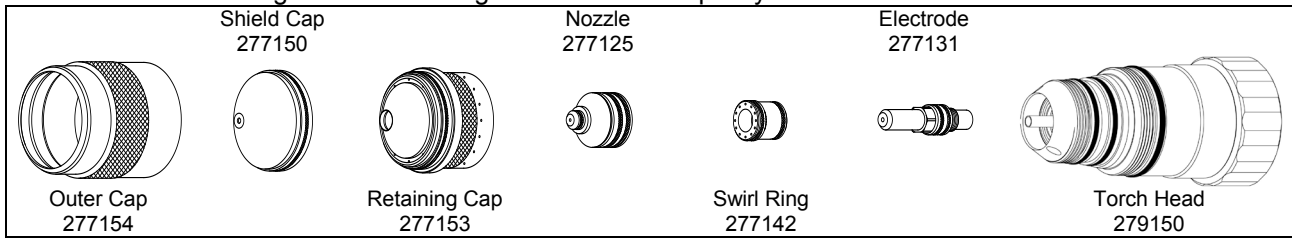

Imperial

Material Thickness		Preflow	Plasma	Shield	Postflow	Arc Voltage	Travel Speed	Cutting Height	Pierce Height	Pierce Time	Kerf Width
(ga)	(in)	(psi)	(psi)	(psi)	(psi)	(volts)	(ipm)	(in)	(in)	(msec)	(in)
10	.135	25	80	25	79	132	120	.060	.150	200	.085
	3/16					134	100	.070	.200	300	
	1/4					140	75	.090	.225	400	.090
	3/8					148	50	.120	.250	500	

Metric

Material Thickness		Preflow	Plasma	Shield	Postflow	Arc Voltage	Travel Speed	Cutting Height	Pierce Height	Pierce Time	Kerf Width
(mm)	(mm)	(psi)	(psi)	(psi)	(psi)	(volts)	(mm/m)	(mm)	(mm)	(msec)	(mm)
3		25	80	25	79	131	3210	1.4	3.3	200	2.2
5	134					2445	1.8	5.1	400		
6	138					2050	2.1	5.5		2.3	


Marking

Material Thickness			Preflow	Plasma	Shield	Postflow	Arc Voltage	Travel Speed		Marking Height		Initial Height		Pierce Time
(ga)	(in)	(mm)	(psi)	(psi)	(psi)	(psi)	(volts)	(ipm)	(mm/min)	(in)	(mm)	(in)	(mm)	(msec)
All Thicknesses			N/A	28	25	N/A	135	250	6350	.096	2.4	.100	2.5	0

* Use an arc transfer height (ignition height) of .150" (3.8 mm) for cutting and .100" (2.5 mm) for marking
(Revised 10/22/2009)

Stainless Steel - 100 Amps - H17 Plasma / Nitrogen Shield Copper Electrode

This gas combination gives the best cut quality and minimum dross levels

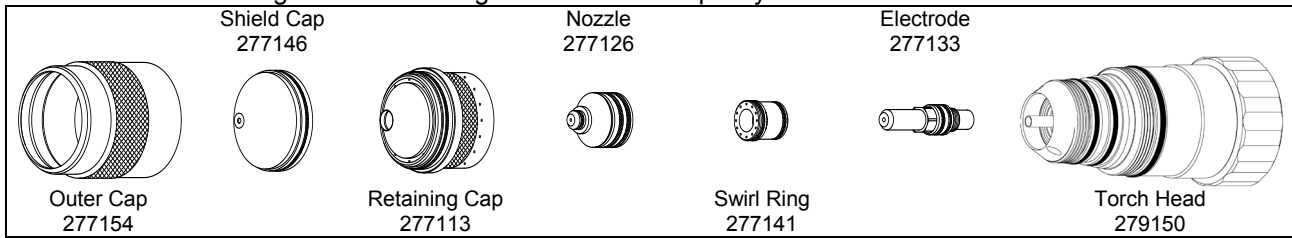

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)
3/16	28	67	46	67	138	115	.105	.200	300	.100
1/4					140	100	.125	.225	400	
3/8					152	65	.180	.250	500	

Metric

Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
5	28	67	46	67	138	2865	2.7	5.1	400	2.5
6					139	2625	3.0	5.5		2.7


Marking

Material Thickness (ga) (in) (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm) (mm/min)	Marking Height (in) (mm)	Initial Height (in) (mm)	Pierce Time (msec)
All Thicknesses	N/A	28	25	N/A	130	250 6350	.100 2.5	.100 2.5	0

* Use an arc transfer height (ignition height) of .200" (5.1 mm) for cutting and .100" (2.5 mm) for marking
(Revised 12/1/09)

Stainless Steel - 100 Amps - Air Plasma / Nitrogen Shield Copper Electrode

This gas combination gives medium cut quality and minimum dross levels

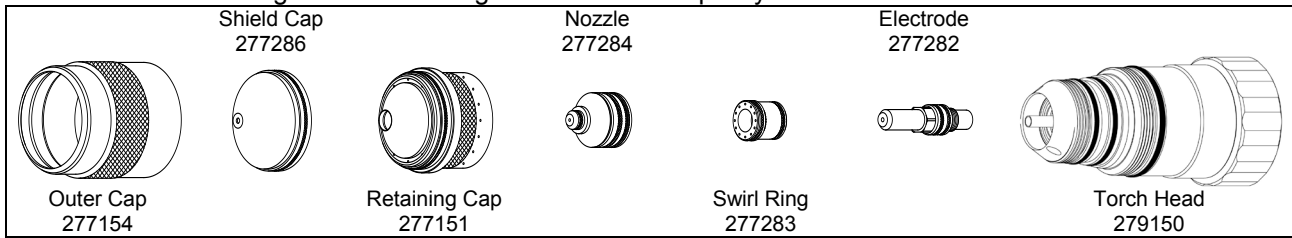

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)
1/4	25	94	35	93	141	100	.135	.225	400	.092
3/8					147	80	.170	.250	500	
1/2					154	55	.210	.300	600	

Metric

Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
6	25	94	35	93	140	2595	3.2	5.6	400	2.3
10					148	1935	4.4	6.5	600	2.4
12					152	1540	5.0	7.3		


Marking

Material Thickness			Preflow	Plasma	Shield	Postflow	Arc Voltage	Travel Speed		Marking Height		Initial Height		Pierce Time
(ga)	(in)	(mm)	(psi)	(psi)	(psi)	(psi)	(volts)	(ipm)	(mm/min)	(in)	(mm)	(in)	(mm)	(msec)
All Thicknesses			N/A	28	25	N/A	130	250	6350	.100	2.5	.100	2.5	0

* Use an arc transfer height (ignition height) of .200" (5.1 mm) for cutting and .100" (2.5 mm) for marking
(Revised 10/21/2009)

Stainless Steel - 150 Amps – H17 Plasma / Nitrogen Shield Copper Electrode

This gas combination gives the best cut quality and minimum dross levels

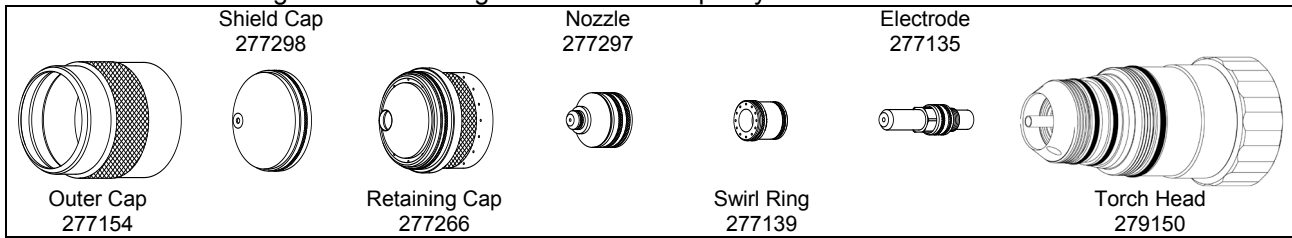

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)
1/4	25	81	75	81	165	95	.250	.250	400	.135
3/8						75	.150	.275	500	
1/2						60	.165	.300	600	.140
5/8						50	.185	.325	800	
3/4						40	.250	.350	1200	

Metric

Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
10	25	81	75	81	155	1845	3.8	7.0	600	3.4
12						1610	4.1	7.4		3.6
16						1260	4.7	8.3	800	
20					167	940	6.9	9.0	1200	3.7


Marking

Material Thickness (ga) (in) (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm) (mm/min)	Marking Height (in) (mm)	Initial Height (in) (mm)	Pierce Time (msec)
All Thicknesses	N/A	28	25	N/A	135	250 6350	.100 2.5	.100 2.5	0

* Use an arc transfer height (ignition height) of .200" (5.1 mm) for cutting and .100" (2.5 mm) for marking
(Revised 12/01/09)

Stainless Steel - 150 Amps - Air Plasma / Nitrogen Shield Copper Electrode

This gas combination gives medium cut quality and minimum dross levels

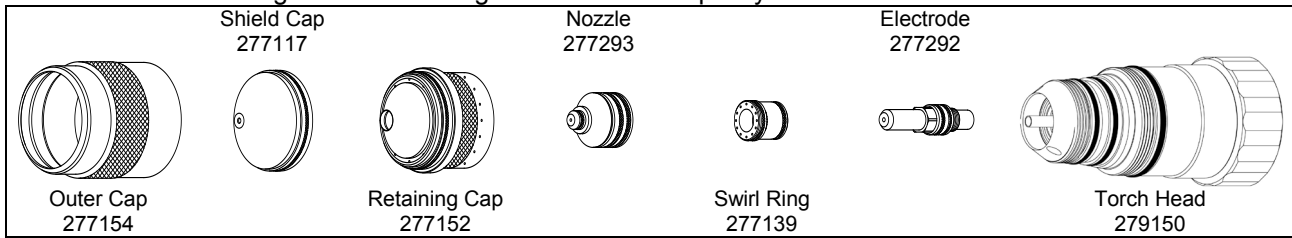

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)
1/4	25	75	70	67	145	150	.160	.250	400	.125
3/8					150	115	.180	.275	500	
1/2					155	85	.210	.300	600	.130
5/8					160	60	.220	.325	800	
3/4					168	45	.240	.350	1200	

Metric

Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
6	25	75	70	67	144	3910	4.0	6.3	400	3.2
10					150	2805	4.7	7.0	600	
12					153	2330	5.1	7.4	3.3	
16					160	1510	5.6	8.3		
20					170	1030	6.2	9.0		1200


Marking

Material Thickness (ga) (in) (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm) (mm/min)	Marking Height (in) (mm)	Initial Height (in) (mm)	Pierce Time (msec)
All Thicknesses	N/A	28	25	N/A	135	250 6350	.100 2.5	.100 2.5	0

* Use an arc transfer height (ignition height) of .200" (5.1 mm) for cutting and .100" (2.5 mm) for marking (Revised 12/01/2009)

Stainless Steel - 200 Amps - H17 Plasma / Nitrogen Shield Copper Electrode

This gas combination gives the good cut quality and minimum cross levels

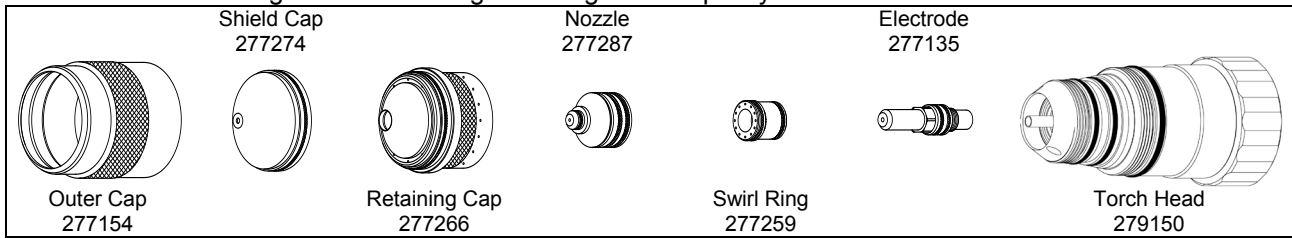

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)
3/8	37	68	85	68	156	80	.195	.250	500	.150
1/2					148	75	.130	.300	600	
5/8					155	60	.190	.350	800	.155
3/4					160	50	.200	.400	1200	
1.0					170	35	.240	.450	1500	

Metric

Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
10	37	68	85	68	154	2010	4.7	6.5	600	3.8
12					149	1935	3.6	7.3		
16					155	1515	4.8	8.9	800	3.9
20					161	1215	5.2	10.3	1500	
25					169	915	6.0	11.3		

Marking


Material Thickness			Preflow	Plasma	Shield	Postflow	Arc Voltage	Travel Speed		Marking Height		Initial Height		Pierce Time
(ga)	(in)	(mm)	(psi)	(psi)	(psi)	(psi)	(volts)	(ipm)	(mm/min)	(in)	(mm)	(in)	(mm)	(msec)
All Thicknesses			N/A	28	25	N/A	120	250	6350	.100	2.5	.100	2.5	0

* Use an arc transfer height (ignition height) of .200" (5.1 mm) for cutting and .100" (2.5 mm) for marking
(Revised 12/01/2009)

This information is subject to the controls of the Export Administration Regulations [EAR]. This information shall not be provided to non-U.S. persons or transferred by any means to any location outside the United States contrary to the requirements of the EAR.

Stainless Steel - 200 Amps - Air Plasma / Nitrogen Shield Copper Electrode

This gas combination gives medium cut quality and minimum dross levels

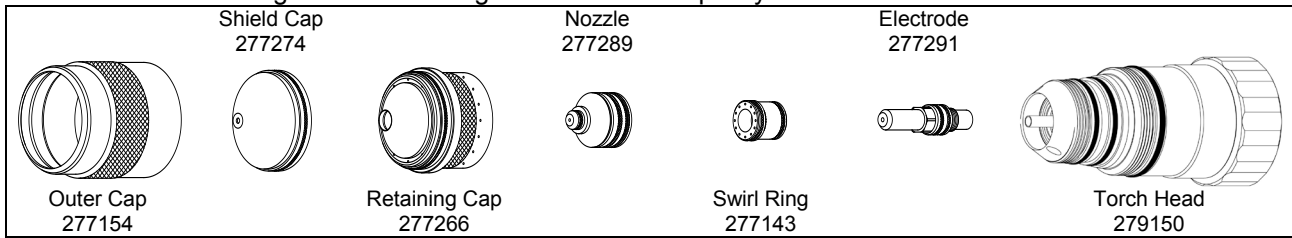

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)
1/4	20	82	58	75	130	200	.070	.200	400	.150
3/8					133	150		.250	500	
1/2					140	110	.115	.300	600	.152
5/8					146	75	.150	.350	800	
3/4					153	60	.190	.400	1200	.155
1.0					158	40	.210	.450	1500	
1.25 **					170	20	.250	.350		.165
1.50 **					180	10	.275	.350	.175	

Metric

Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
6	20	82	58	75	129	5220	1.8	4.9	400	3.8
10					134	3655	1.9	6.5	600	
12					138	3020	2.6	7.3		3.9
16					146	1890	3.8	8.9	800	
20					153	1450	4.8	10.3	1500	4.1
25					157	1050	5.2	11.3		
32 **					170	495	6.4	8.9		
38 **					179	260	6.9	8.9		

Marking

Material Thickness (ga) (in) (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm) (mm/min)	Marking Height (in) (mm)	Initial Height (in) (mm)	Pierce Time (msec)
All Thicknesses	N/A	25	25	N/A	120	250 6350	.100 2.5	.100 2.5	0

* Use an arc transfer height (ignition height) of .200" (5.1 mm) for cutting and .100" (2.5 mm) for marking


** Edge start recommended

(Revised 12/01/2009)

This information is subject to the controls of the Export Administration Regulations [EAR]. This information shall not be provided to non-U.S. persons or transferred by any means to any location outside the United States contrary to the requirements of the EAR.

Stainless Steel - 260 Amps - H17 Plasma / Nitrogen Shield Copper Electrode

This gas combination gives the best cut quality and minimum dross levels

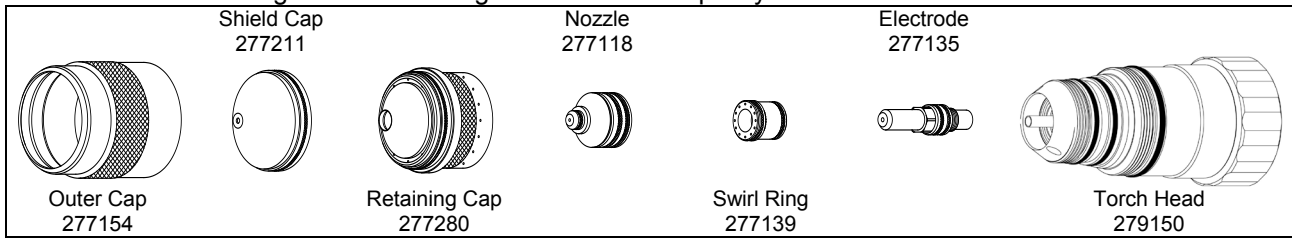

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)
3/8	40	63	70	63	145	85	.160	.250	500	.190
1/2					142	80	.140	.300	600	
5/8					145	65	.185	.350	800	.195
3/4					150	55	.225	.400	1200	
1.0					160	33	.250	.450	1500	.200
1.25 **					170	26	.280	.350		.205

Metric

Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
10	40	63	70	63	144	2140	4.0	6.5	600	4.8
12					142	2060	3.7	7.3		
16					145	1640	4.7	8.9	800	5.0
20					151	1315	5.8	10.3		
25					159	875	6.3	11.3	1500	5.1
32 **					170	650	7.1	8.7		5.2

Marking


Material Thickness (ga) (in) (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm) (mm/min)	Marking Height (in) (mm)	Initial Height (in) (mm)	Pierce Time (msec)
All Thicknesses	N/A	28	25	N/A	108	250 6350	.100 2.5	.100 2.5	0

* Use an arc transfer height (ignition height) of .250" (6.4 mm) for cutting and .100" (2.5 mm) for marking

** Edge start recommended
(Revised 12/01 /2009)

Stainless Steel - 275 Amps - Air Plasma / Nitrogen Shield Copper Electrode

This gas combination gives medium cut quality and minimum dross levels

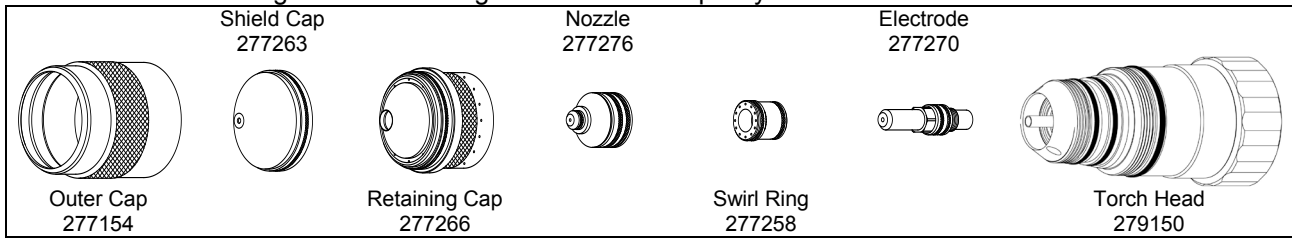

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)
1/2	20	93	70	83	143	120	.125	.300	600	.165
5/8					148	90	.140	.350	800	
3/4					152	80	.180	.400	1200	.170
1.0					165	55	.210	.450	1500	
1.25 **					175	35	.250	.350		
1.50 **					185	25	.300	.350		

Metric

Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
12	20	93	70	83	141	3220	3.1	7.3	600	4.2
16					148	2275	3.6	8.9	800	
20					153	1940	4.7	10.3	1500	4.3
25					164	1435	5.2	11.3		
32 **					175	880	6.4	8.9		
38 **					184	640	7.5	8.9		4.6

Marking


Material Thickness (ga) (in) (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm) (mm/min)	Marking Height (in) (mm)	Initial Height (in) (mm)	Pierce Time (msec)
All Thicknesses	N/A	28	25	N/A	108	250 6350	.100 2.5	.100 2.5	0

* Use an arc transfer height (ignition height) of .250" (6.4 mm) for cutting and .100" (2.5 mm) for marking

** Edge start recommended

(Revised 10/22/2009)

Aluminum - 30 Amps - Air Plasma / Nitrogen Shield Copper Electrode

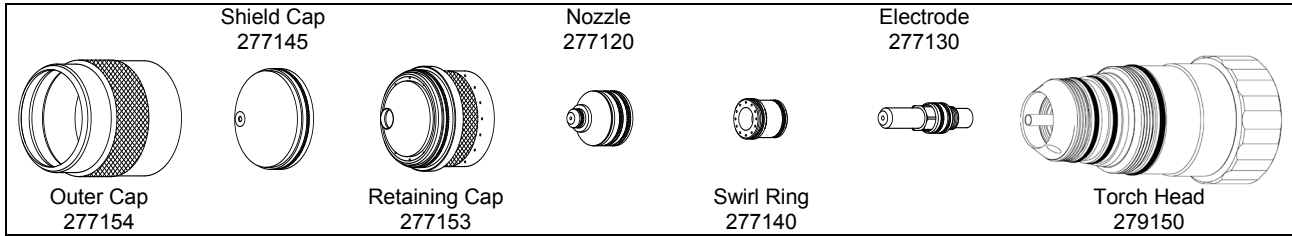

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)
.040	30	92	20	90	135	150	.030	.100	100	.065
.050						120				
.063						90				

Metric


Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
1	30	92	20	90	135	3885	0.8	2.5	100	1.7
1.5						2520				

Marking

Material Thickness			Preflow	Plasma	Shield	Postflow	Arc Voltage	Travel Speed		Marking Height		Initial Height		Pierce Time
(ga)	(in)	(mm)	(psi)	(psi)	(psi)	(psi)	(volts)	(ipm)	(mm/min)	(in)	(mm)	(in)	(mm)	(msec)
All Thicknesses			N/A	28	25	N/A	145	250	6350	.177	4.5	.100	2.5	0

* Use an arc transfer height (ignition height) of .100" (2.5 mm) for cutting and .100" (2.5 mm) for marking (Revised 12/01/2009)

Aluminum - 50 Amps - Air Plasma / Nitrogen Shield Copper Electrode

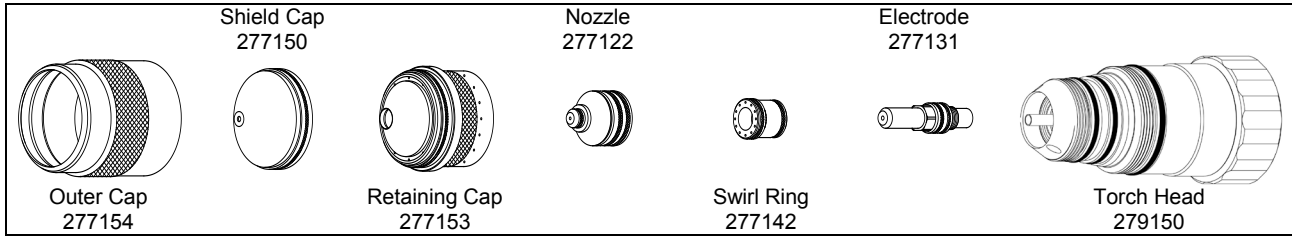

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)
.050	25	74	19	73	135	180	.050	.100	100	.080
.063					138	140	.065		150	.082
.080					143	90	.075	.150	200	.085

Metric


Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
1.5	25	74	19	73	137	3870	1.5	2.5	150	2.1
2.0					142	2360	1.8	3.7	200	2.2

Marking

Material Thickness (ga) (in) (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm) (mm/min)	Marking Height (in) (mm)	Initial Height (in) (mm)	Pierce Time (msec)
All Thicknesses	N/A	28	25	N/A	145	250 6350	.147 3.7	.100 2.5	0

* Use an arc transfer height (ignition height) of .100" (2.5 mm) for cutting and .100" (2.5 mm) for marking (Revised 10/21/2009)

Aluminum - 70 Amps - Air Plasma / Nitrogen Shield Copper Electrode

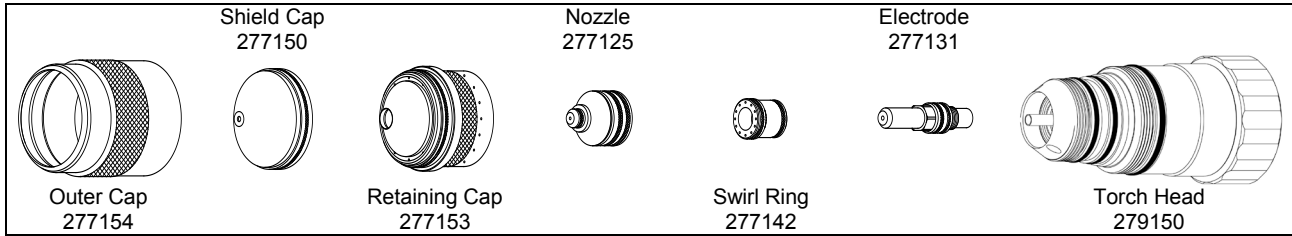

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)
.080	25	80	25	79	130	250	.050	.150	100	.080
1/8					135	160	.070	.175		
3/16					145	80	.100	.200	200	.085
1/4					150	50	.060	.250	300	
3/8					155	40	.075	.275	400	.090
1/2					162	30	.115	.300	500	

Metric


Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
2	25	80	25	79	129	6400	1.2	3.7	100	2.0
3					134	4420	1.7	4.3		
5					145	1920	2.3	5.2	300	2.2
6					148	1440	1.7	6.1		
10					156	975	2.0	7.0	500	2.3
12					160	820	2.6	7.4		

Marking

Material Thickness (ga) (in) (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm) (mm/min)	Marking Height (in) (mm)	Initial Height (in) (mm)	Pierce Time (msec)
All Thicknesses	N/A	28	25	N/A	135	250 6350	.096 2.4	.100 2.5	0

* Use an arc transfer height (ignition height) of .150" (3.8 mm) for cutting and .100" (2.5 mm) for marking (Revised 10/22/2009)

Aluminum - 100 Amps - Air Plasma / Nitrogen Shield Copper Electrode

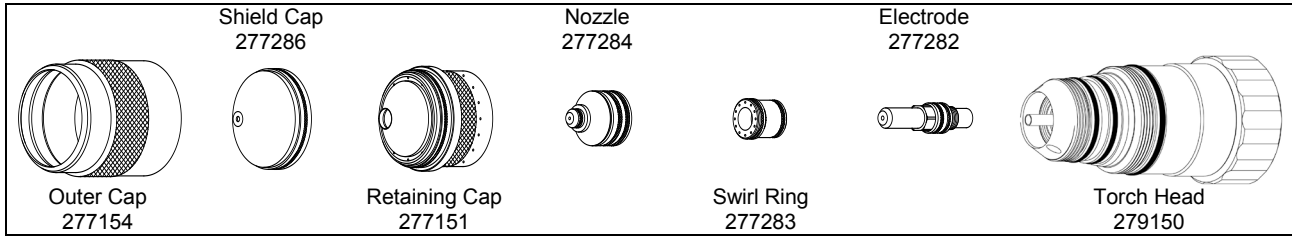

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)
1/4	25	94	26	93	158	105	.155	.250	300	.095
3/8					162	90	.180	.275	400	.098
1/2					165	70	.195	.300	500	.100

Metric


Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
6	25	94	26	93	158	2710	3.8	6.3	300	2.4
10					162	2210	4.6	7.0	500	2.5
12					165	1890	4.9	7.4		

Marking

Material Thickness (ga) (in) (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm) (mm/min)	Marking Height (in) (mm)	Initial Height (in) (mm)	Pierce Time (msec)
All Thicknesses	N/A	28	25	N/A	130	250 6350	.100 2.5	.100 2.5	0

* Use an arc transfer height (ignition height) of .250" (6.4 mm) for cutting and .100" (2.5 mm) for marking (Revised 02/23/2010)

Aluminum - 150 Amps - Air Plasma / Nitrogen Shield Copper Electrode

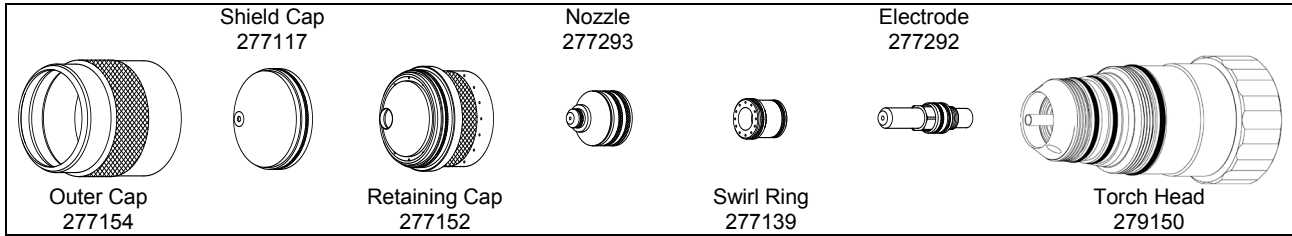

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)
1/4	25	75	50	67	145	145	.130	.250	400	.125
3/8					155	115	.185	.275	500	
1/2					165	90	.230	.300	600	.130
5/8					170	65	.250	.325	800	.135
3/4					45	.350	1200	.140		

Metric


Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
6	25	75	50	67	143	3770	3.1	6.3	400	3.2
10					156	2825	4.8	7.0	600	
12					162	2430	5.5	7.4	3.3	
16					170	1630	6.4	8.3	3.4	
20					170	990	9.0	1200	3.6	

Marking

Material Thickness			Preflow	Plasma	Shield	Postflow	Travel Speed		Marking Height		Initial Height		Pierce Time	
(ga)	(in)	(mm)	(psi)	(psi)	(psi)	(psi)	(ipm)	(mm/min)	(in)	(mm)	(in)	(mm)	(msec)	
All Thicknesses			N/A	28	25	N/A	135	250	6350	.100	2.5	.100	2.5	0

* Use an arc transfer height (ignition height) of .250" (6.4 mm) for cutting and .100" (2.5 mm) for marking (Revised 12/01/2009)

Aluminum - 200 Amps - Air Plasma / Nitrogen Shield Copper Electrode

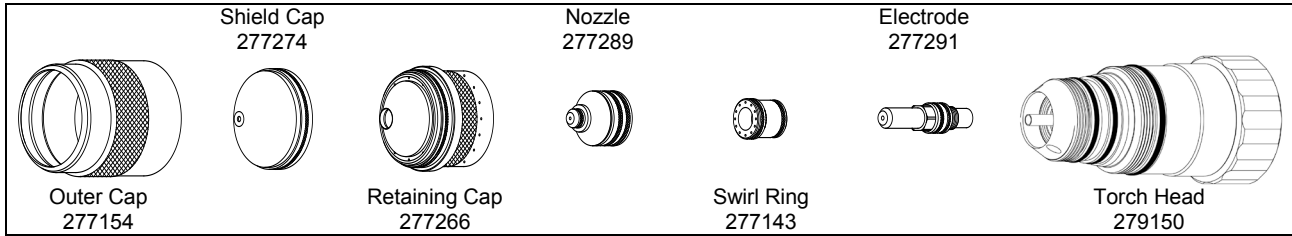

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)
1/4	20	82	58	75	150	190	.135	.250	300	.150
3/8					155	145	.140	.275	400	
1/2						110	.135	.300	500	
5/8					160	95	.135	.350	600	
3/4						65	.150	.400	800	
1.0 **					175	35	.200	.400	1000	.170

Metric

Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
6	20	82	58	75	149	4955	3.3	6.3	300	3.8
10					155	3545	3.5	7.0	500	
12						2995	3.4	7.4	800	
16					160	2380	3.9	8.9	800	
20					162	1575	3.9	10.2	1000	
25 **					174	940	5.0	10.2	1000	4.3


Marking

Material Thickness (ga) (in) (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm) (mm/min)	Marking Height (in) (mm)	Initial Height (in) (mm)	Pierce Time (msec)
All Thicknesses	N/A	28	25	N/A	120	250 6350	.100 2.5	.100 2.5	0

* Use an arc transfer height (ignition height) of .250" (6.4 mm) for cutting and .100" (2.5 mm) for marking

** Edge start recommended
(Revised 10/21/2009)

Aluminum - 275 Amps - Air Plasma / Nitrogen Shield Copper Electrode

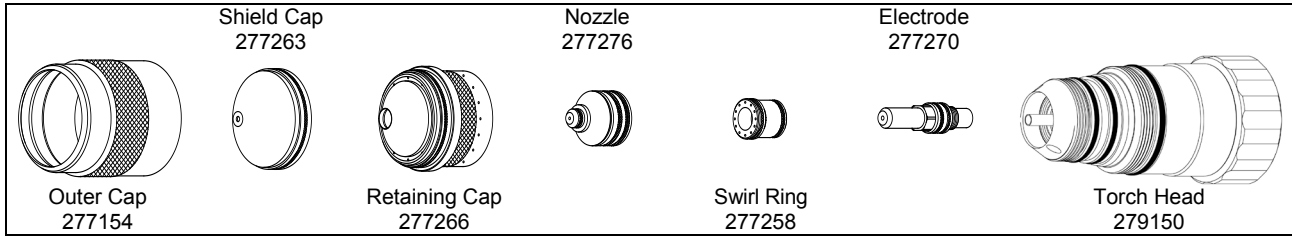

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)
3/8	20	93	65	83	160	160	.160	.275	400	.160
1/2					165	125	.180	.300	500	
5/8					168	105	.190	.350	600	.165
3/4					172	85	.200	.400	800	
1.00 **					180	60	.240		1000	.170
1.25 **					185	45	.260			
1.50 **					190	25	.270	.180		

Metric


Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
10	20	93	65	83	160	3930	4.1	7.1	500	4.1
12					163	3375	4.4	7.4		
16					168	2645	4.8	8.9	800	4.2
20					173	2055	5.3	10.2		
25 **					179	1565	6.0		1000	4.3
32 **					185	1120	6.6			
38 **					189	645	6.8	4.6		

Marking

Material Thickness (ga) (in) (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm) (mm/min)	Marking Height (in) (mm)	Initial Height (in) (mm)	Pierce Time (msec)
All Thicknesses	N/A	28	25	N/A	108	250 6350	.100 2.5	.100 2.5	0

* Use an arc transfer height (ignition height) of .275" (7.0 mm) for cutting and .100" (2.5 mm) for marking
 ** Edge start recommended
 (Revised 10/22/2009)

Mild Steel - 200 Amps – Oxygen Plasma / Air Shield Silver Electrode

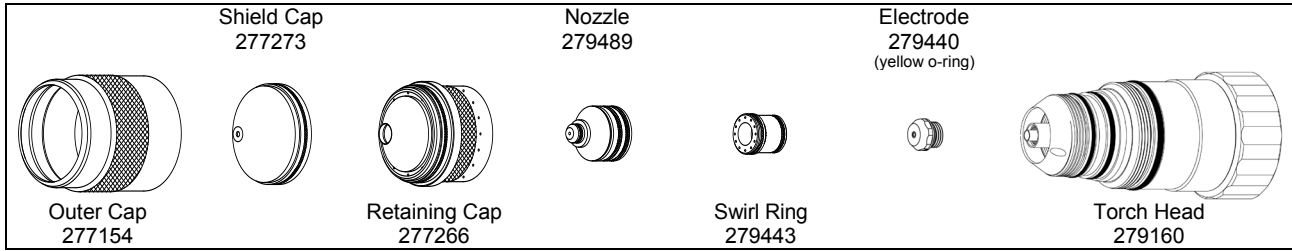

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)
1/4	20	82	58	75	125	230	.040	.200	300	.150
3/8					130	140	.090	.250	400	
1/2					133	120	.115	.300	500	
5/8					137	100	.130	.350	600	.152
3/4					140	75	.150	.400	800	
1					147	50	.175	.450	1000	.155
1.25					155	25	.240	.500	1500	
1.5 **					165	17	.300	.350		
1.75 **					175	12	.350	.500		
2.0 **					185	7	.500	.500		.160

Metric

Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
6	20	82	58	75	124	6100	.8	4.9	300	3.8
10					130	3480	2.3	6.5	500	
12					132	3160	2.7	7.3	800	
16					137	2515	3.3	8.9	1000	3.9
20					141	1810	3.8	10.3	1000	
25					146	1310	4.3	11.3	1500	4.0
32					155	610	6.1	12.7		
38 **					164	435	7.5	8.9		
45 **					175	295	9.2	9.2		
50 **					183	195	12.2	12.2		4.1

Marking

Material Thickness (ga) (in) (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm) (mm/min)	Marking Height (in) (mm)	Initial Height (in) (mm)	Pierce Time (msec)
All Thicknesses	N/A	28	28	N/A	120	250 6350	.100 2.5	.100 2.5	0


* Use an arc transfer height (ignition height) of .200" (5.1 mm) for cutting and .100" (2.5 mm) for marking

** Edge start recommended

(Revised 12/01/09)

This information is subject to the controls of the Export Administration Regulations [EAR]. This information shall not be provided to non-U.S. persons or transferred by any means to any location outside the United States contrary to the requirements of the EAR.

Mild Steel - 275 Amps - Oxygen Plasma / Air Shield Silver Electrode

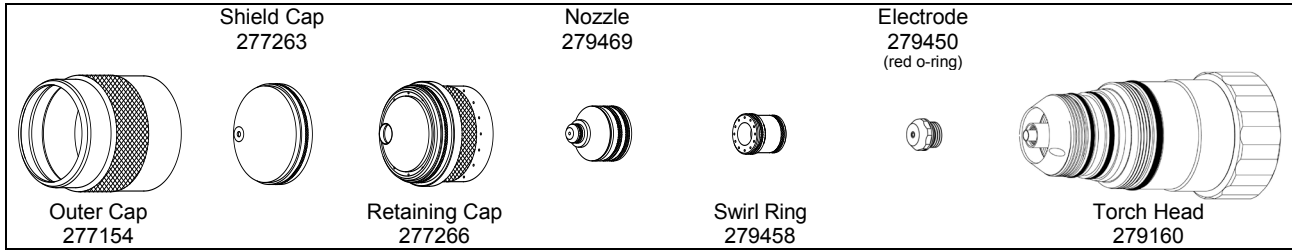

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)
1/2	20	93	70	83	139	125	.140	.300	500	.165
5/8						105	.135	.325	600	
3/4					138	90	.120	.350	800	.170
1										
1.25					150	45	.175	.500	1500	.190
1.50 **										
1.75 **					170	20	.290	.375	.275	
2.00 **										180
2.25 **					185	13	.375	.385		
2.50 **									190	9

Metric

Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
12	20	93	70	83	139	3290	3.6	7.4	500	4.2
16						2650	3.3	8.3	800	
20					138	2190	3.1	9.0	1000	4.3
25										
32					150	1120	4.4	12.8	1500	4.8
38 **										
45 **					170	495	7.5	9.2	6.9	
50 **										178
55 **					183	345	9.2	9.6		
60 **									187	285

Marking


Material Thickness (ga) (in) (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm) (mm/min)	Marking Height (in) (mm)	Initial Height (in) (mm)	Pierce Time (msec)
All Thicknesses	N/A	28	28	N/A	108	250 6350	.100 2.5	.100 2.5	0

* Use an arc transfer height (ignition height) of .300" (7.6 mm) for cutting and .100" (2.5 mm) for marking
 ** Edge start recommended.
 (Revised 10/22/09)

This information is subject to the controls of the Export Administration Regulations [EAR]. This information shall not be provided to non-U.S. persons or transferred by any means to any location outside the United States contrary to the requirements of the EAR.

Stainless Steel - 200 Amps - Air Plasma / Nitrogen Shield Silver Electrode

This gas combination gives medium cut quality and minimum dross levels

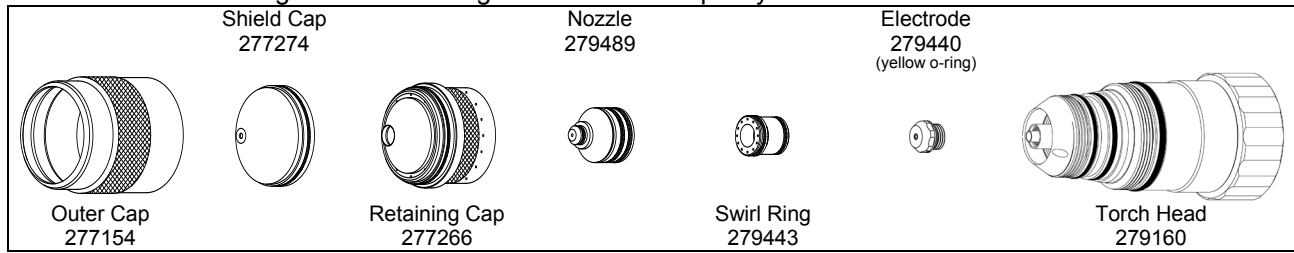

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)	
1/4	20	82	58	75	130	200	.070	.200	400	.150	
3/8					133	150		.250			500
1/2					140	110		.115	.300		600
5/8					146	75	.150	.350	800	.155	
3/4					153	60	.190	.400			1200
1.0					158	40	.210	.450	1500	.160	
1.25 **					170	20	.250	.350			.165
1.50 **					180	10	.275	.350			.175

Metric

Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
6	20	82	58	75	129	5220	1.8	4.9	400	3.8
10					134	3655	1.9	6.5		
12					138	3020	2.6	7.3	800	3.9
16					146	1890	3.8	8.9		
20					153	1450	4.8	10.3	1500	4.1
25					157	1050	5.2	11.3		
32 **					170	495	6.4	8.9		
38 **					179	260	6.9	8.9	4.4	

Marking

Material Thickness (ga) (in) (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm) (mm/min)	Marking Height (in) (mm)	Initial Height (in) (mm)	Pierce Time (msec)
All Thicknesses	N/A	25	25	N/A	120	250 6350	.100 2.5	.100 2.5	0


* Use an arc transfer height (ignition height) of .200" (5.1 mm) for cutting and .100" (2.5 mm) for marking

** Edge start recommended

(Revised 12/01/2009)

This information is subject to the controls of the Export Administration Regulations [EAR]. This information shall not be provided to non-U.S. persons or transferred by any means to any location outside the United States contrary to the requirements of the EAR.

Aluminum - 200 Amps - Air Plasma / Nitrogen Shield Silver Electrode

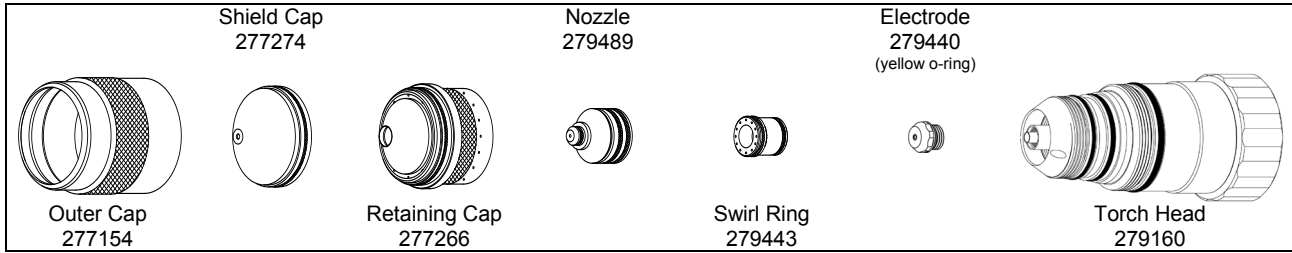

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)
1/4	20	82	58	75	150	190	.135	.250	300	.150
3/8					155	145	.140	.275	400	
1/2						110	.135	.300	500	.155
5/8					95	.350	600			
3/4					160	.150	.400	800	.160	
1.0 **					175	.200	1000	.170		

Metric

Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
6	20	82	58	75	149	4955	3.3	6.3	300	3.8
10					155	3545	3.5	7.0	500	
12						2995	3.4	7.4	800	3.9
16					160	2380	3.4	8.9		
20					162	1575	3.9	10.2	1000	4.1
25 **					174	940	5.0	4.3		

Marking

Material Thickness (ga) (in) (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm) (mm/min)	Marking Height (in) (mm)	Initial Height (in) (mm)	Pierce Time (msec)
All Thicknesses	N/A	28	25	N/A	120	250 6350	.100 2.5	.100 2.5	0


* Use an arc transfer height (ignition height) of .250" (6.4 mm) for cutting and .100" (2.5 mm) for marking

** Edge start recommended

(Revised 10/21/2009)

This information is subject to the controls of the Export Administration Regulations [EAR]. This information shall not be provided to non-U.S. persons or transferred by any means to any location outside the United States contrary to the requirements of the EAR.

Aluminum - 275 Amps - Air Plasma / Nitrogen Shield Silver Electrode

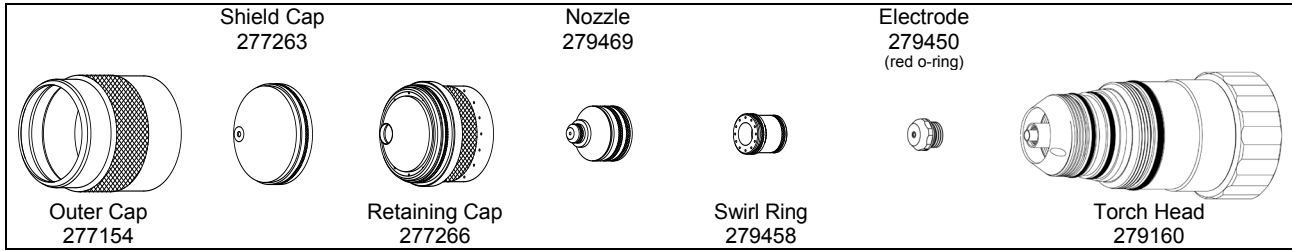

Imperial

Material Thickness (in)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm)	Cutting Height (in)	Pierce Height (in)	Pierce Time (msec)	Kerf Width (in)	
3/8	20	93	65	83	160	160	.160	.275	400	.160	
1/2					165	125	.180	.300	500		
5/8					168	105	.190	.350	600	.165	
3/4					172	85	.200	.400	800		
1.00 **					180	60	.240		1000		.170
1.25 **					185	45	.260	190	25	.270	.180

Metric

Material Thickness (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (mm/m)	Cutting Height (mm)	Pierce Height (mm)	Pierce Time (msec)	Kerf Width (mm)
10	20	93	65	83	160	3930	4.1	7.1	500	4.1
12					163	3375	4.4	7.4		
16					168	2645	4.8	8.9	800	4.2
20					173	2055	5.3	10.2		
25 **					179	1565	6.0			
32 **					185	1120	6.6			
38 **					189	645	6.8	4.6		

Marking

Material Thickness (ga) (in) (mm)	Preflow (psi)	Plasma (psi)	Shield (psi)	Postflow (psi)	Arc Voltage (volts)	Travel Speed (ipm) (mm/min)	Marking Height (in) (mm)	Initial Height (in) (mm)	Pierce Time (msec)
All Thicknesses	N/A	28	25	N/A	108	250 6350	.100 2.5	.100 2.5	0

* Use an arc transfer height (ignition height) of .275" (7.0 mm) for cutting and .100" (2.5 mm) for marking

** Edge start recommended

(Revised 10/22/2009)

This information is subject to the controls of the Export Administration Regulations [EAR]. This information shall not be provided to non-U.S. persons or transferred by any means to any location outside the United States contrary to the requirements of the EAR.

BLANK PAGE